

**НАУЧНО ИЗСЛЕДОВАТЕЛСКИ ИНСТИТУТ
ПО СТРОИТЕЛНИ МАТЕРИАЛИ – ЕООД**

www.niism.com

1528 София, ул. "Илия Бешков" 1

тел.: +359 2/ 973 27 87, 873 76 88, факс: 973 29 10

1528 Sofia, I. Beshkov Str. 1, PK 60

e-mail: niism@abv.bg, niism@niism.com

RESEARCH INSTITUTE OF BUILDING MATERIALS
DIRECTION CONSTRUCTION PRODUCTS CONFORMITY ASSESSMENT
TESTING LABORATORY
Notification № CPD 05 – NB 1950/17.09.2007

Page 1 of 2

CERTIFIED Laboratory from BAS according to BDS EN/IEC 17025:2006
Certificate reg. 47 ЛИ Valid until 01.07.2018

TEST REPORT

**FOR INITIAL TYPE-TESTING OF PRODUCT
UNDER SYSTEM 3**

№ ITT-EC-292-7 / 09.09.2014

1. WATERPROOFING COATINGS.

TWOCOMPONENT WATERPROOFING COATING POLYMER-CEMENT BASED.

Commercial name – BK – Hidrostop 5/5.

Manufacturer: BANJA KOMERC BEKAMENT D.O.O., Arandjelovac, Republic Serbia.

(name of the product)

2. BANJA KOMERC BEKAMENT D.O.O., Arandjelovac, Republic Serbia.

Application ref.№ AIL - 03 - 1060/25.06.2014.

The sample is delivered by the Applicant.

(name of the Applicant, Number and date of the protocol for sample taking)

3. Testing method: BDS EN 14891:2012, BDS EN 206-1/HA: 2008, ILM.

(standards number or approved interlaboratory methods)

4. Date of sample receiving / samples for testing in the laboratory: 25.06.2014,
lab. № 108.

5. Sample quantity for testing: component A + component B = 10 kg .
(quantity and weight of the samples)

6. Date of the test execution: 25.06 – 05.09.2014.

TL Head

(RA eng. M. Kostova)

Manager:

(eng. Vasko Dimitrov)



7. TEST RESULTS

7.1 Test result in the scope of accreditation

№	Name of the index	Unit	Standard, approved methods	Test results (value, indefiniteness)	Value and tolerances of the method index	Testing conditions	Deviation of the test method
1	2	3	4	5	6	7	8
1.	Watertightness at 150 kPa	-	Interlaboratory method* BDS EN 14891:2012 BDS EN 206-1 / HA:2008	Pass: No penetration	BDS EN 14891:2012 No penetration ≤20 g. weight gain	t = 23 °C	No

3

Note I: If it is necessary, the test report could include opinions and interpretations for certain tests (conclusions are not allowed), only in compliance with the requirements of item 5.10.5 from BDS EN ISO/IEC 17025.

Note II: The results of the testing are valid only for the tested samples. The test report conclusions cannot be multiplied without the written agreement of the Testing Laboratory.

*The test pieces are made according to interlaboratory method and their dimensions are in conformity with the relative standard test methods.

The present protocol shall serve the manufacturer/importer for conformity declaration issuing and to place conformity mark.


THE TEST WAS EXECUTED BY:

(eng. St. Todorova, technologist N. Seliktar)

TL HEAD:

(RA eng. M. Kostova)



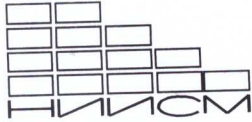

® НАУЧНО-ИЗСЛЕДОВАТЕЛСКИ ИНСТИТУТ
ПО СТРОИТЕЛНИ МАТЕРИАЛИ

RESEARCH INSTITUTE OF BUILDING MATERIALS

1528 СОФИЯ, ул. "ИЛИЯ БЕШКОВ" 1

тел.: 973 27 87; 873 76 88; факс: 973 29 10

CONSTRUCTION PRODUCTS TESTING LABORATORY

Tel. +359 2 973 29 52.

e-mail: niism.abv.bg

Page 1 of 3

TEST REPORT

№ 1113-1 / 09.09.2014

1. WATERPROOFING COATINGS.

TWOCOMPONENT WATERPROOFING COATING POLYMER-CEMENT BASED.

Commercial name – BK – Hidrostop 5/5.

Manufacturer: BANJA KOMERC BEKAMENT D.O.O., Arandjelovac, Republic Serbia.

(name of the product)

2. BANJA KOMERC BEKAMENT D.O.O., Arandjelovac, Republic Serbia.

Application ref. № AIL - 03 - 1060/25.06.2014.

The sample is delivered by the Applicant.

(name of the Applicant, Number and date of the protocol for sample taking)

3. Testing method: BDS EN ISO 2811-1:2011, BDS EN ISO 3251:2008, BDS EN ISO 2431+AC: 2001, BDS EN 787-9:1999, BDS EN 1097-3:2000, BDS EN 1015-1:2001, BDS EN 1849-2:2010, BDS EN 12311-2:2010, BDS EN 14891:2012, BDS EN 206-1/HA:2008.

(standards number or approved interlaboratory methods)

4. Date of sample receiving / samples for testing in the laboratory:
25.06.2014, lab. № 108.

5. Sample quantity for testing: component A + component B = 10 kg .
(quantity and weight of the samples)

6. Date of the test execution: 25.06 – 05.09.2014.

HEAD OF ACCREDITED LABORATORY:

(RA eng. M. Kostova)



7. TEST RESULTS

No	Name of the index	Unit	Standard, approved methods	No of the sample in the register book	Test results (value, indefiniteness)	Value and tolerances of the method index	Testing conditions	Deviation of the test method
1	2	3	4	5	6	7	8	9
<u>Identification indexes</u>								
<u>COMPONENT B</u>								
1.	Density	g/cm ³	BDS EN ISO 2811-1: 2011	1113-1	1,01	-	t = 23 °C	No
2.	Non-volatile matter content	%	BDS EN ISO 3251: 2008	1113-1	28,03	-	t = 23 °C	No
3.	Flow time by use of flow cups: - ø 4 mm - ø 6 mm	s	BDS EN ISO 2431 + AC:2001	1113-1	14 8	-	t = 23 °C	No
4.	Ph value	-	BDS EN ISO 787-9: 1999	1113-1	6,5	-	t = 23 °C	No
<u>COMPONENT A</u>								
5.	Bulk density	kg/m ³	BDS EN 1097-3: 2000	1113-1	1360	-	t = 23 °C	No
6.	Particle size distribution (by sieve analysis) 0,5 mm 0,25 mm 0,125 mm 0,063 mm Fibre content	%	BDS EN 1015-1: 2001	1113-1	99,1 68,2 43,7 39,8 ~1,0	-	t = 23 °C	No
7.	Proportion of the components A:B	parts by weight	-	1113-1	1:1	Value declared by the Manufacturer	t = 23 °C	No
8.	Mass per unit area (at thickness 2 mm)	kg/m ²	BDS EN 1849-2: 2010	1113-1	2,86	-	t = 22 °C	No

1	2	3	4	5	6	7	8	9
9.	Tensile strength • Unreinforced	N/mm ²	BDS EN 12311-2: 2010 Method B	1113-1	0,5	-	t = 23 °C	No
10.	Elongation	%	BDS EN 12311: 2010	1113-1	55	-	t = 23 °C	No
11.	Adhesion strength after curing in normal conditions	N/mm ²	BDS EN 14891: 2012 Annex A	1113-1	1,02	BDS EN 14891:2012 ≥0,5	t = 23 °C	No
12.	Adhesion strength after immersion in water	N/mm ²	BDS EN 14891: 2012 Annex A	1113-1	0,58	BDS EN 14891:2012 ≥0,5	t = 23 °C	No
13.	Adhesion strength after heat ageing at 70 °C	N/mm ²	BDS EN 14891: 2012 Annex A	1113-1	0,83	BDS EN 14891:2012 ≥0,5	t = 70 °C	No
14.	Adhesion strength after freeze-thaw cycles	N/mm ²	BDS EN 14891: 2012 Annex A	1113-1	0,58	BDS EN 14891:2012 ≥0,5	t = -15 °C	No
15.	Adhesion strength after contact with chlorinated water	N/mm ²	BDS EN 14891: 2012 Annex A	1113-1	0,65	BDS EN 14891:2012 ≥0,5	t = 23 °C	No
16.	Crack bridging ability	mm	BDS EN 14891: 2012, Annex A Interlaboratory method*	1113-1	0,95	BDS EN 14891:2012 ≥0,75	t = 23 °C	No
17.	Watertightness	-	BDS EN 14891:2012 BDS EN 206-1 / HA:2008	1113-1	No penetration	BDS EN 14891:2012 No penetration ≤20 g. weight gain 168 hours at 150 kPa	t = 23 °C	No

*The test pieces are made according to interlaboratory method and their dimensions are in conformity with the relative standard test methods.

Note: The results of the testing are valid only for the tested samples. The test report conclusions can not be multiplied without the written agreement of the Testing Laboratory.

THE TEST WAS EXECUTED BY:

(eng. M. Petkov, St. Todorova)

HEAD OF ACCREDITED LABORATORY:

(RA eng. M. Kostova)

